


### CHARACTERISTICS

Hexamethoxymethyl-melamine resin, absorbed on a silica based carrier

### FORM OF DELIVERY

72% active resin as free flowing powder

### TYPICAL STRUCTURE

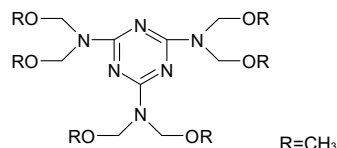

### FIELDS OF APPLICATION

Crosslinker for resorcinol and phenolic novolac resin types for adhesion promoting or reinforcing compounds in rubber applications.

### PROPERTIES

Determined per batch:

Property	Unit	Value
<b>Appearance</b> (Test Method 001)	Passes	White to tan free flowing powder
<b>Ash Residue at 550 °C/2hrs.</b> (Test Method 003)	%	23.5 - 28.0
<b>Moisture</b> (Test Method 002)	%	3.0 max.
<b>Acetone Insolubles</b> (Test Method 068)	%	26.0 - 30.0
<b>Fineness</b> % retained on 100 mesh (Test Method 025)	%	0.10 max.
<b>Free Formaldehyde</b> (Test Method DIN ISO 11402 / Calculated)	%	0.12 max.
<b>Useful Information</b> Not regularly determined		
<b>Density at 25 °C</b>	g/ml	1.4-1.5

### TECHNICAL INFORMATION

Resimene 3520 PJ-72 is a hexamethoxymethyl melamine (HMMM) type resin used as a crosslinking agent for resorcinol or novolac resins and as an adhesion promoter for rubber compounds to steel cord, textiles and other reinforcing materials. This is a 72% active resin, absorbed on a silica based carrier, to provide for a free flowing powder.

Resimene 3520 PJ-72 is used in combination with resorcinol or a novolac resin for increasing compound hardness or for promotion of adhesion between rubber and reinforcing cord or fabrics. Resimene 3520 PJ-72 is suggested as a replacement for hexamethylene-tetramine because of its lower toxicity, absence of amine or ammoniacal by-products and minimal effect on scorch time.

Resimene 3520 PJ-72 is recommended to bond treated cellulose fibers to the rubber matrix. It is non-staining and non-discoloring when used on its own. When used in combination with resorcinol or resorcinol based resins, pink discoloration occurs, which becomes brown on exposure to UV light. However, the compound remains non-staining.

### APPLICATION & PROCESSING

Resimene 3520 PJ-72 is normally used at 1.5 to 4.5 phr (active HMMM) in conjunction with 0.5 to 3.0 phr resorcinol in most elastomers to promote adhesion. It is effective with brass plated steel cord, polyester, rayon, nylon and glass fibers in tire, belting and industrial product applications. Adhesion properties can be enhanced with 5.0 to 10.0 phr silica. For hardness increase levels of resorcinol or Novolac resin can be much higher than those used for adhesion. When Resimene 3520 PJ-72 is used to bond treated cellulose fibers into the rubber matrix, it is usually added at about 1.5 phr (active HMMM) for each 20 to 30 phr of treated cellulose fiber. Resimene 3520 PJ-72 is normally added with the curatives in the final mixing stage. In the presence of resorcinol or novolac resin, the mix temperature should not exceed 100°C. Vulcanization should be taken to maximum modulus to achieve maximum adhesion or hardness.



### STORAGE STABILITY:

At a temperature of 25°C the storage stability of Resimene 3520 PJ-72 packed in original containers amounts to at least 24 months.



Data contained in this publication are based on careful investigations and are intended for information only. Any user is obliged to carry out tests under his own responsibility as to suitability of the product for a particular use and to investigate the possible violation of industrial property rights of third parties. Information is therefore not binding and cannot be construed as guaranteeing specific properties of products as established by law. Any liability as to the exactness and completeness of data is thus excluded. We apply our General Sales Conditions.



	<b>World Area</b>		<b>Customer Support</b>	<b>Technical Support</b>
<b>Prefere Melamines LLC</b> 730 B Worcester Street Springfield, MA 01151, USA	North & South America		+1 888 723 2873	+1 413 730 3810
<b>Prefere Melamines GmbH</b> Alt Fechenheim 34 D-60386 Frankfurt, Germany	Europe, Middle East, Africa Asia		+49 69 6051040 2319	+49 69 6051040 2310 +49 69 6051040 2040
www.prefere.com		E-mail	<a href="mailto:melamines.info@prefere.com">melamines.info@prefere.com</a>	

**NOTICE:** Although the information and recommendations set forth herein (hereinafter "Information") are presented in good faith and believed to be correct as of the date hereof, Prefere Melamines (and its subsidiaries) makes no representations or warranties as to the completeness or accuracy thereof. Information is supplied upon the condition that the persons receiving same will make their own determination as to the suitability for their purpose prior to use. In no event will Prefere Melamines be responsible for damages of any nature whatsoever resulting from the use of or reliance upon Information or the product to which Information refers. Nothing contained herein is to be construed as a recommendation to use any information, product, process, equipment or formulation in conflict with any trademark, copyright, patent or other intellectual property right and Prefere Melamines makes no representation or warranty, express or implied, that the use thereof will not infringe any patent. Certain products may not be regulated or available in some world areas. NO REPRESENTATIONS OR WARRANTIES, EITHER EXPRESS OR IMPLIED INCLUDING WITHOUT LIMITATION ANY IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE OR OF ANY OTHER NATURE ARE MADE HEREUNDER WITH RESPECT TO INFORMATION OR THE PRODUCT TO WHICH INFORMATION REFERS. Where indicated, ® is a Registered Trademark of Prefere Melamines.

Version October 2021